



Hellenic Gas Transmission System Operator S.A.
357-359 Messogion Av., GR 152 31 Halandri
Tel.: 213 088 4000
Fax: 210 674 9504
Email: desfa@desfa.gr

TECHNICAL SPECIFICATION

Doc No : DSF-SPC-PIP-029

Rev. 1

Page 1 of 13


HIGH PRESSURE (HP) TRANSMISSION SYSTEMS

BUTT WELDING STEEL FITTINGS

JUNE 2021

This document is the property of DESFA S.A. and shall not be reproduced, copied or used for any purpose, other than for which it is specially furnished

1	Second Issue	30-06-2021	AK	KM	TPI
0	First Issue	05-04-2011	PQ DPT.		V.G.
REV	DESCRIPTION	DATE	PRPD	CHKD	APVD

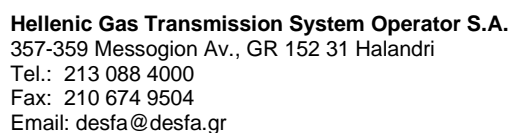

Doc No : DSF-SPC-PIP-029

Rev. 1

Page 2 of 13

[illegible]



Hellenic Gas Transmission System Operator S.A.
357-359 Messogion Av., GR 152 31 Halandri
Tel.: 213 088 4000
Fax: 210 674 9504
Email: desfa@desfa.gr

TECHNICAL SPECIFICATION


Doc No : DSF-SPC-PIP-029

Rev. 1

Page 3 of 13

Table of Contents

1	SCOPE AND OBJECTIVES.....	4
2	REFERENCES	4
3	GENERAL REQUIREMENTS	5

	Hellenic Gas Transmission System Operator S.A. 357-359 Messogion Av., GR 152 31 Halandri Tel.: 213 088 4000 Fax: 210 674 9504 Email: desfa@desfa.gr	TECHNICAL SPECIFICATION
Doc No : DSF-SPC-PIP-029	Rev. 1	Page 4 of 13

1 SCOPE AND OBJECTIVES

1.1 ITEM

Butt welding fittings

1.2 SERVICE

Sweet natural gas with sporadic passage of water and glycol.

1.3 ADDITIONAL INFORMATION

Additional information may be given in the DATA SHEET and Material Requisition and these documents should be read in conjunction with this material specification.

Fitting Vendor shall be responsible to design, fabricate and supply fittings in accordance with the requirements of applicable documents.

In no event, however, dimension, thicknesses, etc., are to be less than those required by standards.

Any conflict between requirements of this specification and drawings, DATA SHEET and Material Requisition supplementary design data, or Codes, shall be referred to Owner, for clarification, before proceeding with fabrication of affected part.

2 REFERENCES

2.1 Reference Documents

2.2 Reference Codes and Standards

(PED) 2014/68/EU

Technical Specification DSF-SPC-QAC-005

[Shop Inspection of Equipment and Materials for NGT Project]

EN ISO 3183

[Petroleum and natural gas industries – Steel Pipe for pipeline transportation systems]

EN ISO 148-1

[Metallic materials. Charpy pendulum impact test. Part 1: Test method]



Hellenic Gas Transmission System Operator S.A.
357-359 Messogion Av., GR 152 31 Halandri
Tel.: 213 088 4000
Fax: 210 674 9504
Email: desfa@desfa.gr

TECHNICAL SPECIFICATION

Doc No : DSF-SPC-PIP-029

Rev. 1

Page 5 of 13

ELOT EN 12732

[Gas infrastructure. Welding steel pipework. Functional requirements]

EN 14870-2

[Petroleum and natural gas industries – Induction bends, fittings and flanges for pipeline transportation systems. Part 2: Fittings]

3 GENERAL REQUIREMENTS

3.1 UNITS

Metric for all units.

3.2 SPECIFICATION

EN14870-2 and additionally satisfying the requirements herein.

3.3 PRESSURE RATING CALCULATIONS

Design calculations shall be in accordance with EN 14870-2

The capability of the fitting to withstand internal pressure shall equal or exceed that of the matching pipe. The verification of the capability shall be made by calculation and/or proof testing as per EN14870-2.

The design calculations and/or results of proof testing shall be available for review.

Refer to Material Requisition DATA SHEET for details of design pressure, design factor, corrosion allowance and abutting pipe dimensions and material specifications.

Elbows, Caps, Reducers and Tees shall have minimum wall thicknesses as per ANNEX A EN14870-2

Corrosion and production allowances shall be added to the calculated wall thickness (including elbows).

3.4 DESIGN PROOF TEST

As per ANNEX B EN14870-2.

3.5 MATERIALS

As per EN14870-2, the starting material for forming into fittings shall be blooms, billets, slabs, forging quality bar, plate, fusion-welded with filler metal or seamless tubular products, produced from fully-killed steels.



Hellenic Gas Transmission System Operator S.A.
357-359 Messogion Av., GR 152 31 Halandri
Tel.: 213 088 4000
Fax: 210 674 9504
Email: desfa@desfa.gr

TECHNICAL SPECIFICATION

Doc No : DSF-SPC-PIP-029

Rev. 1

Page 6 of 13

High-frequency welded (HFW) and helical-seam submerged-arc welding (SAWH) pipes shall not be used.

Fittings shall be manufactured in accordance with a documented MPS (Manufacturing Procedure Specification). Manufacturing shall not proceed until MPS has been accepted by the purchaser

The MPS for the starting material shall specify the following items:

- 1) Name of manufacturer
- 2) Steel-making process
- 3) Steel grade
- 4) Product form and dimensions
- 5) Chemical composition, including that of the weld seam
- 6) Welding procedure specification

Steels requiring preheating for field welding to temperatures higher than 100°C are not acceptable.

Repair by welding is not permitted in the base material.

3.6 CHEMICAL COMPOSITION

As per table 4, EN 14870-2.

3.7 TENSILE PROPERTIES

As per EN14870-2, the tensile properties shall meet the requirements of ISO 3183.

3.8 HEAT TREATMENT

As per EN14870-2, all fittings shall be normalized, normalized and tempered, or quenched and tempered after welding and/or forming.

3.9 TRANSVERSE GUIDED WELD BEND TESTS

Required.

3.10 CHARPY V-NOCH IMPACT TEST

Impact Test as per EN14870-2

Charpy V-noch impact test pieces shall be prepared in accordance with EN ISO 148.

Charpy V-noch test pieces shall be taken from the sample in accordance with EN ISO 3183.

The test temperature shall be -20°C



Hellenic Gas Transmission System Operator S.A.
357-359 Messogion Av., GR 152 31 Halandri
Tel.: 213 088 4000
Fax: 210 674 9504
Email: desfa@desfa.gr

TECHNICAL SPECIFICATION

Doc No : DSF-SPC-PIP-029

Rev. 1

Page 7 of 13

Acceptance criteria shall be according to EN14870-2:

3.11 FITTING DIMENSIONS (SIZE AND WALL THICKNESS)

As per Material Requisition.

3.11.1 REDUCERS

Reducers shaped as conical shells shall have an End-to-End length sufficiently long to permit the half-apex angle of the cone to be 20° or less.

3.11.2 ELBOWS

Unless supplementary requirement SR3 is specified elbows produced by induction bending or by extrusion over mandrel may have straight tangential ends with length of not more than one diameter.

3.12 TOLERANCES OF WELDING FITTINGS

As per EN14870-2, tolerances shall be in accordance with MSS SP-75 and, for nominal sizes less than DN 400, ASME B16.9

3.13 MANUFACTURE

3.13.1 COLD-FORMING TEES. ELBOWS

Cold-forming (except rolling of plates) is not permitted. Tees' outlets shall be produced by extrusion or forging.

Elbows shall be produced either by induction bending of seamless or longitudinally welded pipe, by extrusion over mandrel of seamless pipe, or by welding together of two identical, hot-formed shells.

Caps shall be seamless.

3.13.2 WELDING

Welding qualifications and procedures shall be in accordance with **ELOT EN 15614**.

Hardness of the weld seam and heat affected zone shall nowhere exceed 260HV10.

Repair by welding in parent material is not permitted.

3.14 NON DESTRUCTIVE EXAMINATION

3.14.1 STARTING MATERIALS

Plates and welded pipe shall be ultrasonically scanned to **EN 10253-2**, or equivalent



Hellenic Gas Transmission System Operator S.A.
357-359 Messogion Av., GR 152 31 Halandri
Tel.: 213 088 4000
Fax: 210 674 9504
Email: desfa@desfa.gr

TECHNICAL SPECIFICATION

Doc No : DSF-SPC-PIP-029

Rev. 1

Page 8 of 13

approved standard. Plate or welded pipe intended as starting material for tees shall be 100% continuously ultrasonically scanned for laminations and other discontinuities over surfaces to be extruded. Recording of any discontinuity condition shall render plate or pipe as rejected.

Seamless pipe shall be ultrasonically scanned to **ELOT EN 10208-2** or equivalent approved standard.

External and accessible internal surfaces of tees and elbows either extruded over mandrel or induction bent shall be magnetic particle examined as follows:

3.14.2 TEES, ELBOWS

Over entire extruded area.

In four bands, each 100 mm wide and extending from one end to the other parallel with elbow's axis.

The bands shall be placed along outside, inside, top and bottom of the elbow.

For forgings method and acceptance standards shall be as **EN 10253-2**, however, linear indications are unacceptable.

3.14.3 WELDS

All joints shall be radiographed and found acceptable in accordance with **ELOT EN 12732**.

However, where radiography is unfit for detection of defects, joints shall be ultrasonically examined as per **ELOT EN 12732**.

Where radiography or ultrasonic examination is unfit for detection then magnetic particle examination maybe used as per **ELOT EN 12732**.

3.14.4 WELDING ENDS

All welding ends shall be examined for laminations or other discontinuities to a minimum distance of 50 mm from and including the bevel with a non- destructive method capable of detecting discontinuities extending into the bevel and having a transverse dimension exceeding 6 mm. Any such discontinuity shall be unacceptable.

3.15 MARKING

Additionally, to the marking specified in EN14870-2 each fitting shall be marked with an item number and the Third Party Inspector's or Notified Body stamp if the fittings are following under the (PED) 2014/68/EU

Full traceability shall be ensured between test reports and item numbers.

The purchase order identification shall be the Client Supply Order Number. This number shall be die stamped.



Hellenic Gas Transmission System Operator S.A.
357-359 Messogion Av., GR 152 31 Halandri
Tel.: 213 088 4000
Fax: 210 674 9504
Email: desfa@desfa.gr

TECHNICAL SPECIFICATION

Doc No : DSF-SPC-PIP-029

Rev. 1

Page 9 of 13

3.16 SURFACE TREATMENT

3.16.1 INTERNAL

Untreated free of dirt-grease oil, etc.

3.16.2 EXTERNAL

Soluble rust-preventive varnish.

3.17 SUPPLEMENTARY REQUIREMENTS

3.17.1 GENERAL

The following Supplementary Requirements (SR1 to SR4) shall not apply unless specifically requested on the applicable Data Sheet.

Further requirements, if specifically mentioned in the Material Requisition or on the DATA SHEET, shall be valid. In case of conflict between such requirements and the requirements contained herein, the former shall prevail.

3.17.2 SUPPLEMENTARY REQUIREMENTS - SR1

Tees run pipe or elbows, as may be the case, shall have a bore throughout the body $> 0.96 \times$ inside diameter of abutting pipe. The bore shall be proved on each item by passing a gauging plate or sphere with diameter as required above. The tolerance on plate/sphere diameter shall be $+ 1$ mm.

3.17.3 SUPPLEMENTARY REQUIREMENTS-SR2

Tees shall be furnished with guide bars as per attachment 1 for scraper passage in accordance with Table 1 below.

The guide bars shall be welded together with two crossrails that shall be fixed to the branch wall by fillet welds. All edges that may be rubbed by scrapers shall be rounded with radius equal to one-half the bar thickness. Guide bars shall be mounted flush with the bore of the run and shall further have their ends shaped so that they follow the contour of the outlet as closely as possible. Guide bars and cross-rails shall be made of killed carbon steel.



Hellenic Gas Transmission System Operator S.A.
 357-359 Messogion Av., GR 152 31 Halandri
 Tel.: 213 088 4000
 Fax: 210 674 9504
 Email: desfa@desfa.gr

TECHNICAL SPECIFICATION

Doc No : DSF-SPC-PIP-029

Rev. 1

Page 10 of 13

B	1050	900	W _t	h	750	700	650	600	550	500	450	400	350
DN 50	—	—	—	—	—	—	—	—	—	—	—	—	—
DN 100	8	30	—	—	—	—	—	—	—	—	—	—	2
DN 150	8	35	—	—	—	—	—	—	2	2	2	2	2
DN 200	8	40	—	—	2	2	2	2	2	2	2	2	3
DN 250	8	50	—	2	2	2	2	2	2	2	3	3	3
DN 300	10	55	2	2	2	2	2	2	3	3	3	3	3
DN 350	10	55	3	3	3	3	3	3	3	3	3	3	3
DN 400	10	60	3	3	3	3	3	3	3	3	3	3	—
DN 450	10	65	3	3	3	3	3	3	3	3	3	—	—
DN 500	10	70	3	3	3	3	3	3	3	3	—	—	—
DN 550	15	70	3	3	3	3	3	3	3	—	—	—	—
DN 600	15	75	3	3	3	3	3	3	—	—	—	—	—
DN 650	15	80	3	3	3	3	3	—	—	—	—	—	—
DN 700	15	85	3	3	3	3	—	—	—	—	—	—	—
DN 750	15	90	4	4	4	—	—	—	—	—	—	—	—
DN 900	20	100	4	4	—	—	—	—	—	—	—	—	—
DN 1050	20	120	5	—	—	—	—	—	—	—	—	—	—

No. of bars

B = Nominal branch dia.(mm)


R = Nominal run diameter (mm)

wt = Guide bar wall thickness

h = Guide bar height

TABLE 1

REQUIRED NUMBER OF GUIDE BARS AND GUIDE BAR DIMENSIONS (mm)

 <p>DESFA Hellenic Gas Transmission System Operator S.A.</p>	<p>Hellenic Gas Transmission System Operator S.A. 357-359 Messogion Av., GR 152 31 Halandri Tel.: 213 088 4000 Fax: 210 674 9504 Email: desfa@desfa.gr</p>	<p>TECHNICAL SPECIFICATION</p>
<p>Doc No : DSF-SPC-PIP-029</p>	<p>Rev. 1</p>	<p>Page 11 of 13</p>

All fillet welds shall be dye-penetrant examined and any indication shall be cause for rejection.

3.17.4 SUPPLEMENTARY REQUIREMENTS-SR3

The curvature of the elbows shall continue right to the weld ends, i.e. elbows shall not have tangential ends or transition zones in which mechanical properties (e.g. hardness) may be influenced by the on setting or termination of bending operation.

3.17.5 SUPPLEMENTARY REQUIREMENTS - SR4

Notch toughness shall be satisfied according to para 2.10 at test temperature lower than -20°C, at minimum design temperature as mentioned in Material Requisition.

3.18 TECHNICAL DOCUMENTATION

3.18.1 QUANTITY

Four copies of each, inclusive of original, for all documents and certificates. Four copies of each, inclusive of one reproducible, for all drawings.
Also electronic files of all Documents and Certificates must be submitted by Contractor to the Owner.

3.18.2 DOCUMENT REQUIREMENTS

3.18.2.1 WITH TENDER

Statement regarding starting materials, with reference to Material Standards.

Statement regarding manufacturing process for each type of fitting (forming process and subsequent heat treatment).

3.18.2.2 AFTER AWARD OF CONTRACT (BEFORE PRODUCTION)

Dimensional drawings of each item inclusive of material list giving material grades


and certification levels of starting materials etc.

Guide bar arrangements shall be shown in detail for tees ordered with SR2.

Design calculations for each item.

Statement of Standard proposed for ultrasonic scanning of starting materials.

Statement of method and a procedure summary for non destructive examination of welding ends.

 <p>DESFA Hellenic Gas Transmission System Operator S.A.</p>	<p>Hellenic Gas Transmission System Operator S.A. 357-359 Messogion Av., GR 152 31 Halandri Tel.: 213 088 4000 Fax: 210 674 9504 Email: desfa@desfa.gr</p>	<p>TECHNICAL SPECIFICATION</p>
<p>Doc No : DSF-SPC-PIP-029</p>	<p>Rev. 1</p>	<p>Page 12 of 13</p>

Vendor's Detailed Test and Inspection plan.
The plan should additionally show the control points at which the
Independent
Accredited Inspector's witnessing/ approval is required, as per section 5 herein.

3.18.3 ON DELIVERY

Fitting certification package.

3.19 INSPECTION AND CERTIFICATION

Inspection will be performed by a Third Party Accredited Inspection Body to be appointed by OWNER.

Inspection requirements are defined in the following documents.

- a. Material requisition
 - b. Job Spec. DSF-SPC-QAC-005
 - c. Relevant project specifications
 - d. Inspection clauses of Applicable Codes
- Inspection procedures to be followed as detailed in Owner document "Inspection and Test instructions".

3.20 SHIPMENT

Where necessary, fittings shall be supported by temporary stiffeners to avoid distortion damage during transportation and erection.

